

NiO and Ag@NiO Nanomaterials for Enhanced Photocatalytic and Photoluminescence Studies: Green Synthesis Using *Lycopodium Linn.*

K. R. Basavalingaiah¹, Udayabhanu², S. Harishkumar³, G. Nagaraju⁴ and Chikkahanumantharayappa^{5*}

¹Department of Science, Government Polytechnic, Tumkur, Karnataka, India

^{1&5}Department of Physics, Vivekananda Degree College, Bengaluru, Karnataka, India

^{2,3&4}Energy Materials Research Laboratory, Department of Chemistry,
Siddaganga Institute of Technology, Tumkur, Karnataka, India

³Department of Pharmaceutical Chemistry, Kuvempu University, Post-Graduate Centre, Kadur, Karnataka, India

*Corresponding Author

E-Mail: chrayappa@gmail.com

Abstract - NiO and Ag-NiO nano particles were prepared using *Lycopodium* extract as a fuel via solution combustion synthesis (SCS) at 500 °C. From the PXRD, FTIR, UV-DRS studies the synthesized NPs were characterized. The morphologies of the prepared NPs were studied by SEM and TEM analysis. The synthesized NPs were tested for photocatalytic and photoluminescence studies. The PXRD data indicated that the synthesized nanoparticles belong to cubic phase structure and space group Fm-3m. The FTIR spectrum of NiO exhibited the absorption band at 427 cm⁻¹ is associated to Ni-O vibration band. The SEM data revealed that agglomeration was obtained. NiO and Ag-NiO NPs were taken for determine the photocatalytic activity study on methylene blue dye, the results indicated that Ag-NiO NPs exhibited promising photocatalytic activity. This is due to occurrence of Ag particles on the NiO material, which makes the catalyst more sensitive. Furthermore, a photoluminescence study for NiO and Ag-NiO was studied.

Keywords: *Lycopodium*, Ag-NiO, Photocatalytic, Photoluminescence

I. INTRODUCTION

Industrial dyestuff contain one of the largest groups of organic compounds that lead to discoloration of water and cause great loss of aquatic life. The elimination of these colors and other organic materials is a priority for ensuring a safe and clean environment [1]. Over the last decades, photo catalysis has attracted special attention as an economic and environmentally safe option for solving energy and pollution problems [2]. Among various semiconductors showing photocatalytic activity, wide band gap semiconductors such as TiO₂, ZnO, etc. bear tremendous hope in helping ease the energy and environment crisis through effective utilization of solar energy based on photovoltaic and water-splitting devices [3, 4]. Unfortunately, their wide band-gaps do not allow the utilization of visible light, which limit their practical applications. Therefore, it is imperative to develop new kinds of photo catalysts with high activities under visible light in view of the efficient utilization of solar energy.

Nickel oxide (NiO) is an important transition metal oxide with cubic lattice structure. It has attracted increasing

attention owing to potential use in a variety of applications such as: catalysis [5], battery cathodes [6, 7], gas sensors [8], electrochromic films [9] and magnetic materials [10, 11]. It can also be extensively used in dye sensitized photocathodes [12]. It exhibits anodic electrochromism, excellent durability and electrochemical stability, large spin optical density and various manufacturing possibilities [13].

Nanostructured NiO has a wide range of applications as a p-type semiconductor with a stable wide band gap (3.6–4.0 eV) [14], although bulk NiO is an antiferromagnetic insulator [15]. Nano-sized NiO is also used in alkaline batteries [16], electrochemical capacitors [17]. Ag is well-known for its intense interactions with visible-light via the resonance of the oscillations of the free electrons within the particles [18], and is considered as a relatively cheap noble metal.

Photo excited electrons in the conduction band (CB) of a semiconductor can be transferred to the noble metals, which act as electron sinks due to the Schottky barrier at the metal–semiconductor interface, while the holes can remain on the semiconductor surface [19, 20]. The recombination of electrons and holes can therefore be prolonged, and the photocatalytic activity will be improved [21]. In addition, the Plasmon resonance of noble metal nanoparticles (NPs) is expected to enhance absorption of incident photons, which will enhance the photocatalytic efficiency of the semiconductors [22]. Hence, that the NiO nanoparticles are modified with Ag particles may exhibit an enhanced photocatalytic activity.

Herein the synthesis of NiO and Ag-NiO nanoparticles via combustion method using *lycopodium* extract as a fuel. The prepared NPs were characterized using powder X-ray diffraction (PXRD), Fourier transform infrared analysis (FTIR), UV-diffused reflectant spectrum (UVDRS), scanning electron microscopy (SEM) and transmission electron microscopy (TEM) of the NiO NPs. Photocatalytic activity of NiO was examined by photodegradation of methylene blue (MB) under visible light illumination and photoluminescence (PL) study was also carried out.

II. EXPERIMENTAL ANALYSIS

A. Synthesis of NiO and Ag-NiO Nps from Lycopodium: In a typical experiment, synthesis of NiO NPs from Lycopodium linn using solution combustion method. The stoichiometric ratios of Ni (NO₃)₂ and AgNO₃ were mixed with Lycopodium, which acts as Fuel. The Nickel nitrate and Lycopodium extract (5, 10, 15 and 20 mL) were added in a crucible and stirred thoroughly with magnetic stirring for ~10 min. After, the formed homogenous solution was kept in muffle furnace maintained at 500 °C for 5 min to get product. For synthesis of Ag-NiO, The synthesis of NiO-Ag nano composites (NiO-Ag-1%; NiO-Ag-3%; NiO-Ag-5%; NiO-Ag-7%) using 10 mL Lycopodium (optimized fuel).

B. Characterization: The synthesized nanoparticles were characterized by using powder X-ray diffractometer (Rigaku smart Lab). FTIR (Bruker-alpha) to analyse metal oxide bond stretching frequencies. The UV- DRS spectrum of the NPs was measured using UV-Visible spectrophotometer (Lab India-Diffuse reflectance spectra and Cary 60 Agilent technologies-Absorbance spectra). The morphologies of the prepared nanoparticles were scanned using Scanning Electron Microscopy (Hitachi-7000 Table top). Shape and size of the NiO crystallites was determined using transmission electron microscope (JEOL 3010). Photoluminescence studies were recorded using fluorescence spectrophotometer Agilent technology Cary Eclipse).

C. Photo Catalytic Activity: Photo-Reactor "Heber" was purchased from Chennai. The photocatalytic reactor consists of a medium pressure mercury vapor lamp ($\lambda_{max} = 365$ nm, 250W) in a jacketed quartz crystal tube. The heat caused by the lamp was removed from cold water by continuous circulation throughout the jacket. The tube has an inside diameter of 2.3 cm, with an outer diameter of 2.7 cm diameter, which is 37 cm long, 100 ml capacity and is placed around the lamp.

The gap between the mercury lamp and the quartz tube containing pollutant was 6 cm. The uniform distribution of catalytic particles throughout the solution was achieved using air pump [23]. The solution was allowed for constantly bubbled in the dark for 30 minutes to ensure the organization of an adsorption-desorption equilibrium between the photocatalyst and MB previous to irradiation of light source. The suspension 2 mL was withdrawn from the reactor over 30 minutes intervals. Centrifuge the solution using spin win micro centrifuger to remove the NiO NPs from the mixture. The dye concentration of left over aqueous solution was measured using UV-Vis spectrophotometer at 664 nm. The % degradation of the MB is calculated using the equation (i)

$$\% \text{ of degradation} = \frac{C_i - C_f}{C_i} \times 100 \dots\dots (i)$$

Where C_i initial and C_f final dye concentrations in ppm. The photocatalytic experiment was repeated by changing

different parameters such as concentration of dye, catalytic load, pH variation, catalyst recycling, etc.

III. RESULTS AND DISCUSSION

A. PXRD Study: The PXRD patterns of NiO nanoparticles are represented in Fig.1. From the XRD data indicated that NiO NPs has cubic phase structure and space group Fm-3m (no.225) resembles with the standard JCPDS card number 1-1239 [24]. No extra peaks were found in the pattern which indicates that purity of the samples. The average crystallite size was measured to be 14.27 nm for NiO and 14.19 nm for Ag-NiO, respectively.

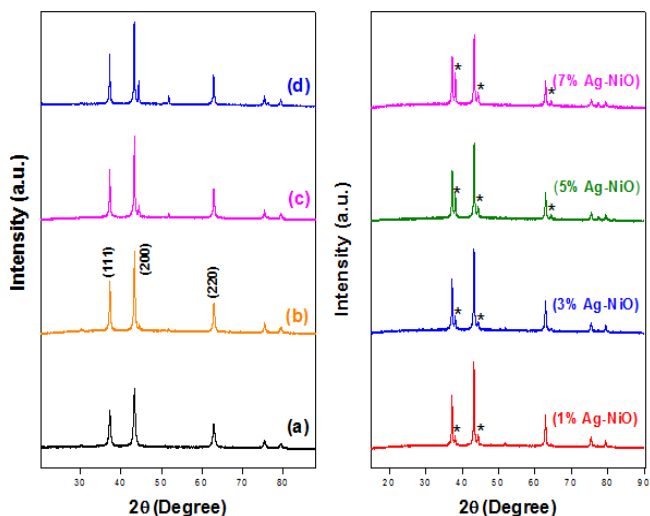


Fig. 1 Powder XRD patterns of the NiO and Ag-NiO nanoparticles

B. FTIR Study: The FTIR spectra of NiO and Ag-NiO nanomaterials were recorded between the ranges of 4000 to 400 cm⁻¹ as shown in Fig 2. Additionally, characteristic bands of NiO, which include the Cu-O symmetric and asymmetric stretching vibrations at 407 cm⁻¹ were also observed [25]. The broad peak at 3435 and 1632 cm⁻¹ is due to the stretching and bending vibrations of -OH, which is due to the absorbed moisture on the surface of the catalyst [26, 27].

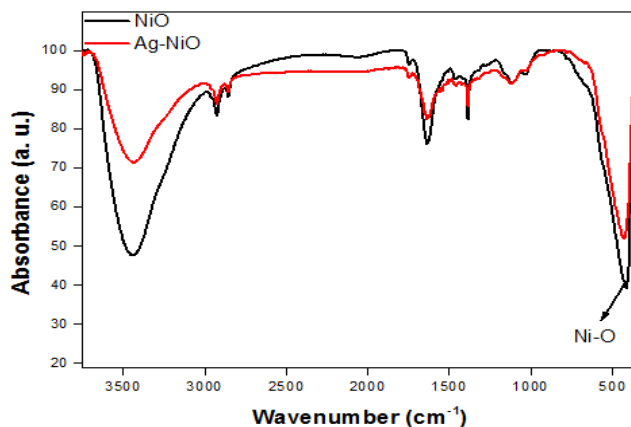


Fig. 2 FTIR spectra of NiO and Ag-NiO Nanoparticles

C. UV-Visible Diffuse Reflectance Studies: (UV-DRS): Fig. 3 shows the UV-Visible spectra of NiO and Ag-NiO NPs synthesized via combustion method using lycopodium extract as a fuel. The spectra demonstrate with absorption

band shown nearly at 300 to 350 nm. Due to electron transfer from valence band to conduction band. The calculated E_g values were found to be 3.79 eV and 3.75 eV for NiO and Ag-NiO NPs respectively [28].

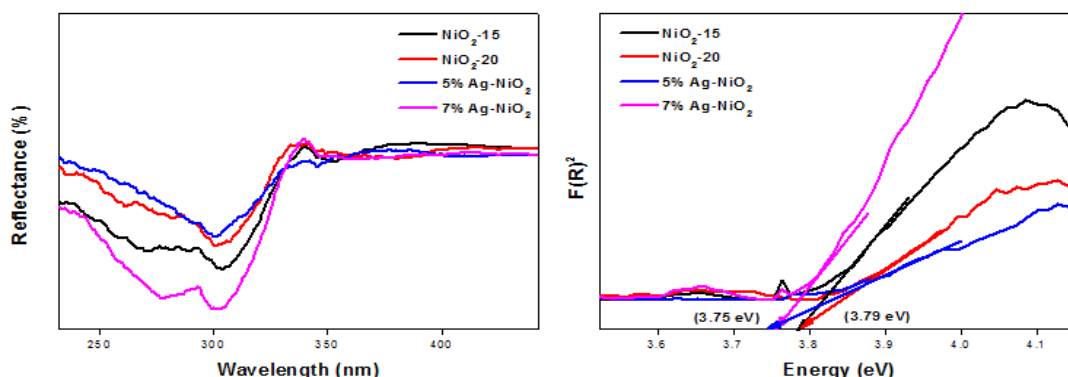


Fig. 3 UV-DRS spectrum of NiO and Ag-NiO NPs

D. Scanning Electron Microscopy (SEM) Studies: Fig. 4 (a, b) represents SEM images of the compound NiO and Fig. 4 (c, d) for Ag- NiO NPs synthesized via combustion method using lycopodium extract as a fuel. The particles are looking like homogenous distribution which is formed by the agglomeration of NPs.

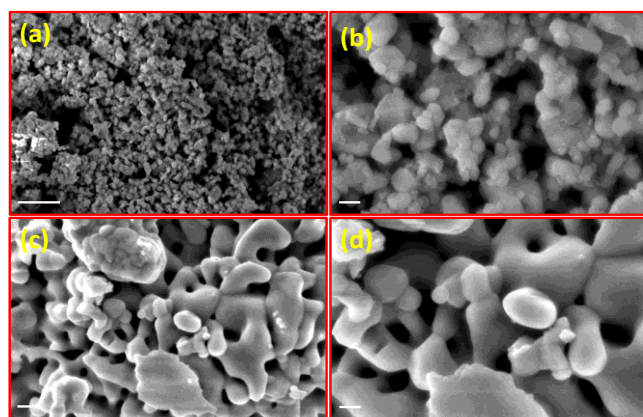


Fig. 4 SEM images of NiO nanomaterials (a) and (b), and Ag-NiO nanomaterials (c) and (d)

E. Transmission Electron Microscopy (TEM) Studies: Fig. 5 shows the TEM images, HR-TEM images and SAED pattern of synthesized Ag- NiO NPs using Lycopodium linn. as a fuel via combustion method. From the TEM images (Fig. 5a, b) we can clearly observe the fine distribution of silver (Ag) on band like nanomaterials. In the Fig.5c the distributed silver (black colored dots) on NiO acquired spherical shape with size of 4.5 to 14.3 nm. The sizes of NiO materials were observed 42 to 76 nm. For NiO, (Fig. 5c) the d-spacing value is 0.15 nm, which belongs to (220) plane. From the SAED pattern, (Fig. 5d) it is confirmed as a polycrystalline in nature. The planes at (111), (200) and (220) planes having highest intensity in XRD and which are matched with bright circular fringes in SAED pattern.

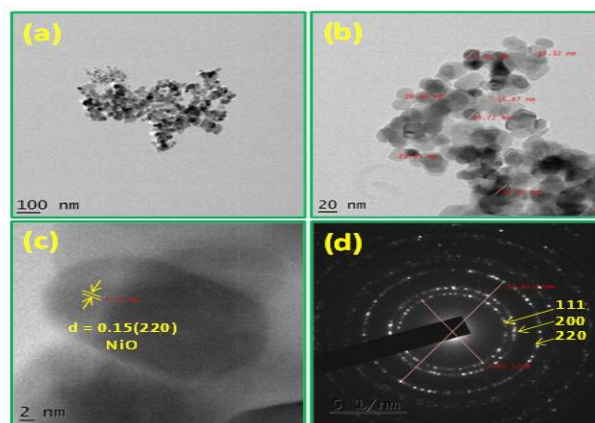


Fig. 5 TEM images (a,b), HR-TEM images (c) and SAED pattern(d) of NiO nanomaterials

IV. PHOTOCATALYTIC DEGRADATION OF NiO AND AG-NiO NPs

Under light radiation, the semiconductor absorbs photons of energy greater than the band gap of semiconductors and then creates electrons and holes in the valence and conducting band. If the charge carriers don't recombine, then they'll travel on the surface wherever free electrons form the reduction of oxygen and form the peroxides and super oxides and created holes oxidize the water and form the OH \cdot ; these generated species are extremely reactive and unstable and ultimately cause to the degradation of organic dyes. Many factors are influencing the Photocatalytic action on dyes, i.e., band gap, surface area, crystallinity, phase composition, surface hydroxyl density, size distribution, morphology, and particle size of the photocatalyst [30]. Prepared NiO NPs were taken as photocatalyst to check the methylene blue dye degradation under UV-light. In every 30 minutes, 2mm of the aliquots sample solution was withdrawn and it was centrifuged and absorption of the samples was recorded. By measuring the change in intensity, we can calculate the degradation rate of dye at λ_{max} -664 nm.

A. Effect of Dye Concentration: The concentration of the dye is playing a crucial role in photocatalytic activity of NiO nanomaterials. Hence, so as to judge the optimum concentration of dye for promising photocatalytic activity, the experiment was carried out by changing the dye concentration of 5-20 ppm under catalytic loading constant (100 mg) and UV light as in Fig.6. This clearly shows that as the dye concentration of 5-20 ppm increases, the photocatalytic degradation is reduced by 80-20% and 20 ppm is the most effective concentration for dye degradation. Generally, as increases the dye concentration, the number of dye molecules is adsorbed on the surface of NiO nanoparticles, so the degradation rate decreases. On the other hand, adsorbed dye molecules were not degraded more rapidly because of the constant light intensity and catalyst loading.

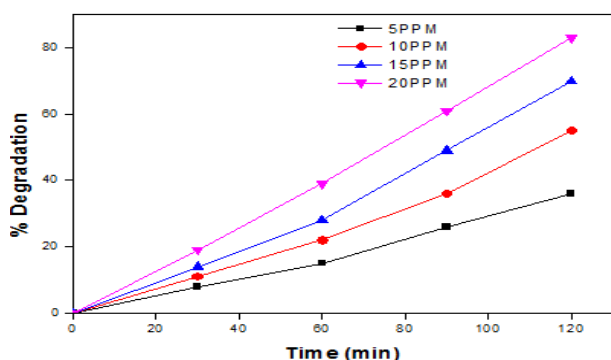


Fig. 6 Degradation MB with varying concentration of dye constant and catalyst load constant

The higher the dye concentration, the smaller the penetration power of light, which means that the photocatalytic decomposition is less at higher concentrations with less occurrence of hydroxyl groups and superoxide radicals [31].

B. Effect of Catalytic Load: Fig.7 represents the graph of MB degradation with varying catalyst load (5-20 mL) by maintaining the constant concentration of dye (100 mL of 5 ppm). The data clearly reveals that as the catalyst load increases over 180 minutes, the rate of dye degradation increases from 70-100%. This is because more active sites are available due to increased catalytic load [31].

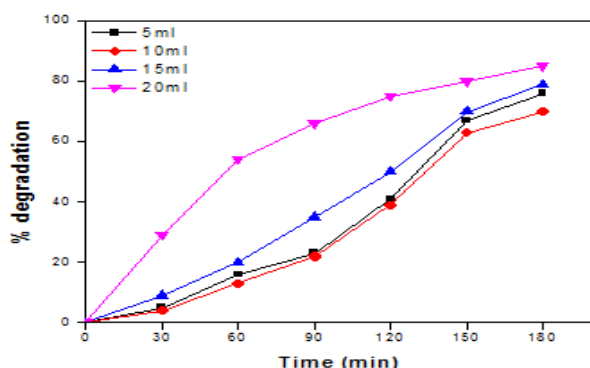


Fig. 7 Degradation of Methylene Blue with varying catalyst load

C. Effect of pH: In order to see the optimum pH for the photolysis of the MB dye, experiments were conducted at completely different pHs (2 and 10) by maintaining the constant catalyst (100 mg) and the dye concentration (5 ppm), and the result represented in Fig.8. This clearly shows that the MB degradation was effective in the basic medium [32, 33] with the very best degradation rate at pH 10. The presence of a large number of OH⁻ ions on the surface of the catalyst can produce less range of OH[•] radicals, that act as primary oxidizing agents and are responsible for the degradation of MB dye [34-38].

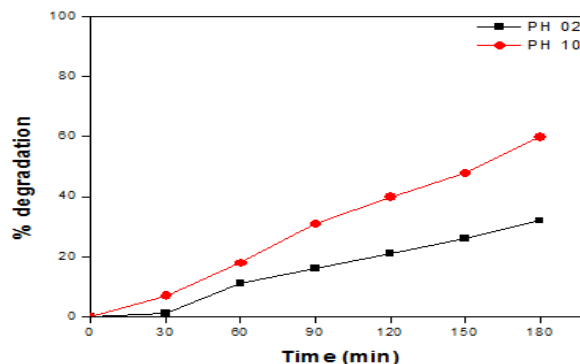


Fig. 8 Degradation of MB with varying pH of the solution and keeping the catalyst load and constant dye constant

D. Catalyst Recycling: To evaluate the stability of the photocatalyst, a recycling experiment was carried out to degradation the methylene blue dye (Fig. 9). The experiment was carried out with 100 mg of catalyst and 100 ml of 5 ppm dye. The decomposition potency of MB was nearly an equivalent for six cycles. This figure clearly shows a reduction in potency of nearly 80% altogether six cycles.

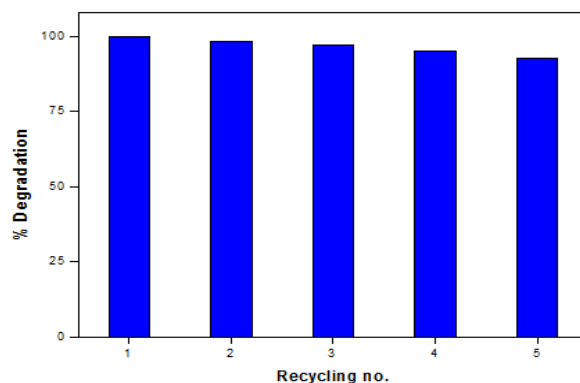



Fig. 9 Recycling of 10 mg of catalyst and 100 ml of 5 ppm dye

E. Mechanism. Scheme: A schematic representation of the degradation of MB using NiO superstructure is shown below.



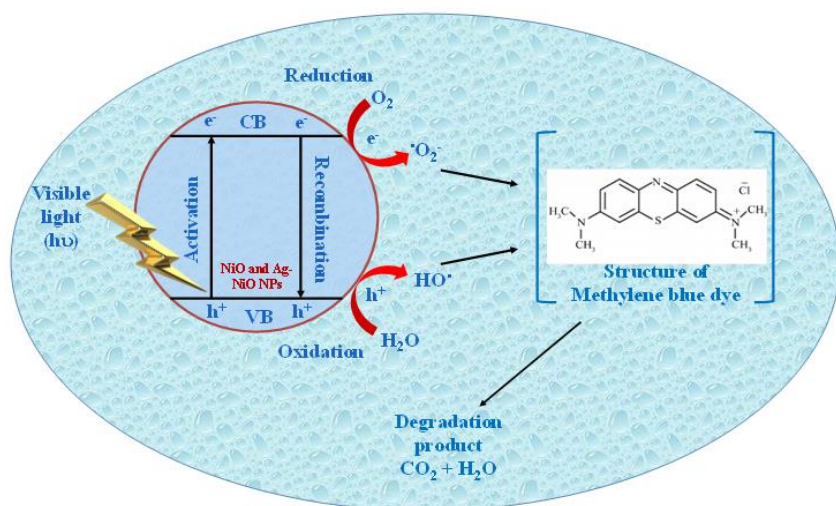


Fig. 10 Graphical representation for the mechanism of NiO under the irradiation of UV-visible light

V. PHOTOLUMINESCENCE STUDIES

PL study is one among the helpful technique for notice the potency of charge carrier separation within the semiconductor [39]. The PL emission spectrum of NiO and Ag- NiO NPs were recorded in room temperature with an excitation wavelength of 271 nm represented in Fig. 10a. The pure NiO Nps provides a strong ultraviolet emission peak at 380 nm. In case of Ag-NiO Nps, the obtained PL emission intensity decreased and the resultant datas are in good agreement with the Stern-Volmer quenching represented in Fig. 11b.

This indicates the efficiency of high charge carrier separation in Ag-NiO NPs. The emission peaks in visible region can be ascribed to bound excitons and defect states positioned at surface of nanostructured pure and doped NiO Nps respectively. Chromaticity coordinates are used to find luminous coloured objects and it can be estimated by Commission International De l'Eclairage (CIE) system. CIE chromaticity diagram of NiO and Ag-NiO Nps represented in Fig. 10c reveals that both the material emit yellow light region [40].

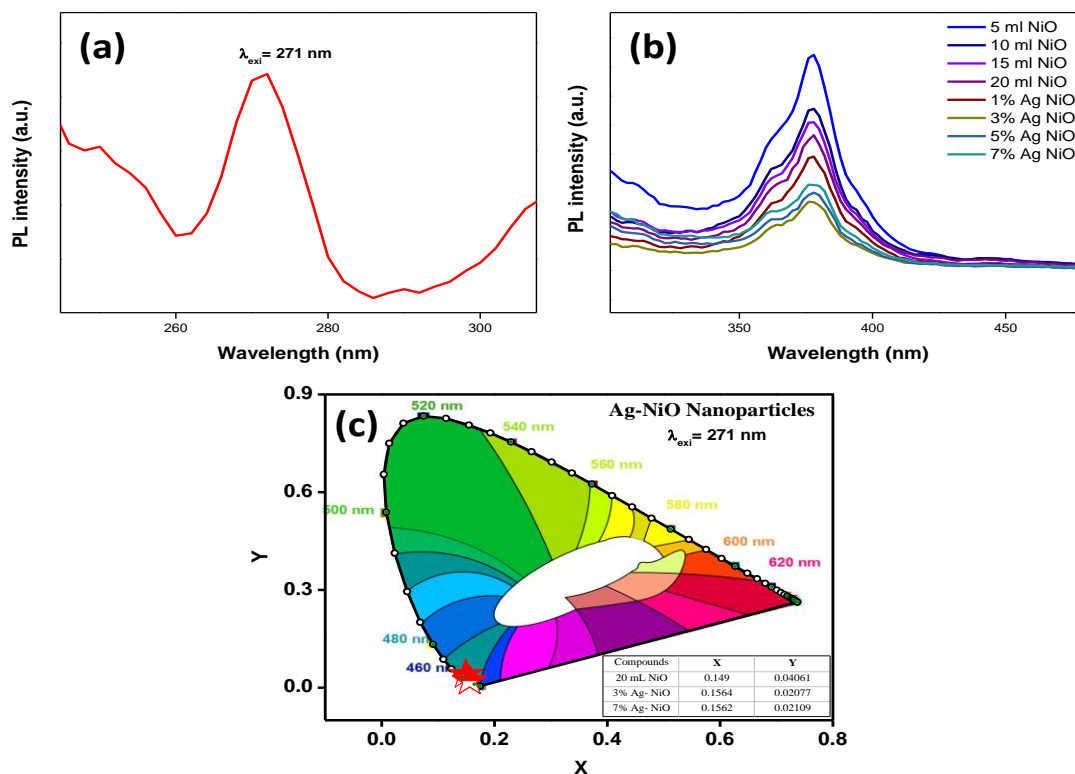


Fig. 11 PL spectrum of NiO and Ag-NiO (a) excitation spectra (b) emission spectra (c) CIE diagram

VI. CONCLUSION

The NiO and Ag-NiO were synthesized by using Lycopodium Linn. Extract as fuel and employing by combustion method. The XRD pattern shows that NiO and Ag-NiO nanoparticles belong to a cubic phase with an average crystallite size of 14.27 nm for NiO and 14.19 nm for Ag-NiO, respectively. The SEM image clearly shows that the Agglomeration of NPs. The TEM image shows that the particles are virtually agglomerated and crystalline. The prepared NiO and Ag-NiO NPs display 80 to 90 % photodegradation activity over methylene blue dye. The photoluminescence study reveals that NiO and Ag-NiO nano particles shown blue color emission.

ACKNOWLEDGEMENT

Mr. Udayabhanu gratefully acknowledge to CSIR-SRF (09/1204(0001)2018-EMR-I). Dr. GN thanks to DST-Nanomission (SR/NM/NS-1262/2013) for financial support. Mr. Basavalingaiah thanks SIT for providing lab facilities.

REFERENCES

[1] M.A. Fox, and M.T. Dulay, "Heterogeneous photocatalysis", *Chemical reviews*, Vol. 93, No.1, pp. 341-357. 1993.

[2] A. Fujishima, and K. Honda, "Electrochemical photolysis of water at a semiconductor electrode", *Nature*, Vol. 238, No. 5358, pp. 37, Jul 1972.

[3] Y. Li, X. Fang, N. Koshizaki, T. Sasaki, L. Li, S. Gao, Y. Shimizu, Y. Bando, and D. Golberg, "Periodic TiO₂ Nanorod Arrays with Hexagonal Nonclose-Packed Arrangements: Excellent Field Emitters by Parameter Optimization", *Advanced Functional Materials*, Vol. 19, No.15, pp. 2467-73, Aug 2009.

[4] Y. Qiu, K. Yan, H. Deng, and S. Yang, "Secondary branching and nitrogen doping of ZnO nanotetrapods: building a highly active network for photoelectrochemical water splitting", *Nano letters*, Vol. 12, No. 1, pp. 407-13, Dec 2011.

[5] K. M. Dooley, S. Y. Chen, and J. R. Ross, "Stable nickel-containing catalysts for the oxidative coupling of methane", *Journal of catalysis*, Vol. 145 No.2, pp.402-8, Feb 1994.

[6] H. X. Yang, Q. F. Dong, and X. H. Hu, "Preparation and characterization of LiNiO₂ synthesized from Ni(OH)₂ and LiOH·H₂O", *Journal of Power Sources*, Vol. 79, No. 2, Jun 1999.

[7] I. Hotový, J. Huran, L. Spiess, R. Čapkovic, and Š. Haščik, "Preparation and characterization of NiO thin films for gas sensor applications", *Vacuum*, Vol. 58, No. 2-3, pp. 300-7. Aug 2000.

[8] E. L. Miller, and R. E. Rocheleau, "Electrochemical behavior of reactively sputtered iron-doped nickel oxide", *Journal of the Electrochemical Society*, Vol. 144, No. 9, pp. 3072-7. Sep 1997.

[9] G. Wang, X. Lu, T. Zhai, Y. Ling, H. Wang, Y. Tong, and Y. Li, "Free-standing nickel oxide nanoflake arrays: synthesis and application for highly sensitive non-enzymatic glucose sensors", *Nanoscale*, Vol. 4, No. 10, pp. 3123-7. 2012.

[10] Y. Wang, J. Zhu, X. Yang, L. Lu, and X. Wang, "Preparation of NiO nanoparticles and their catalytic activity in the thermal decomposition of ammonium perchlorate", *Thermochimica Acta*, Vol. 437, No. 1-2, pp. 106-9. Oct 2005

[11] S. A. Makhlof, F. T. Parker, F. E. Spada, and A. E. Berkowitz, "Magnetic anomalies in NiO nanoparticles", *Journal of applied physics*, Vol. 81, No. 8, pp. 5561-3. Apr 1997.

[12] X. Y. Deng, and Z. Chen, "Preparation of nano-NiO by ammonia precipitation and reaction in solution and competitive balance", *Materials Letters*, Vol. 58, No. 3-4, pp. 276-80. Jan 2004

[13] S. Chakrabarty, and K. Chatterjee, "Synthesis and characterization of nano-dimensional nickelous oxide (NiO) semiconductor", *J. Phys. Sci*, Vol. 13, pp. 245. 2009.

[14] H. Yang, Q. Tao, X. Zhang, A. Tang, and J. Ouyang, "Solid-state synthesis and electrochemical property of SnO₂/NiO nanomaterials", *Journal of alloys and compounds*, Vol. 459, No. 1-2, pp. 98-102, Jul 2008

[15] C. D. Guerra, A. Remn, J. A. Garcia, J. Piqueras, C. Díaz-Guerra, A. Remon, J. A. Garcia, and J. Piqueras, "Cathodoluminescence and photoluminescence spectroscopy of NiO", *Physica Status Solidi (a)*. Vol.163, No.2, pp. 497-503. Oct 1997

[16] J. Bahadur, D. Sen, S. Mazumder, and S. Ramanathan, "Effect of heat treatment on pore structure in nano-crystalline NiO: A small angle neutron scattering study", *Journal of Solid State Chemistry*, Vol. 181, No.5, pp. 1227-35, May 2008

[17] T. Nathan, A. Aziz, A. F. Noor, and S. R. Prabaharan, "Nanostructured NiO for electrochemical capacitors: synthesis and electrochemical properties", *Journal of Solid State Electrochemistry*, Vol. 12, No.7-8, pp. 1003-9. Aug 2008

[18] S. J. Peng, L. L. Li, H. T. Tan, Y. Z. Wu, R. Cai, H. Yu, X. Huang, P. N. Zhu, S. Ramakrishna, M. Srinivasan, and Q. Y. Yan, "Monodispersed Ag nanoparticles loaded on the PVP-assisted synthetic Bi₂O₃CO₃ microspheres with enhanced photocatalytic and supercapacitive performances", *Journal of Materials Chemistry A*, Vol. 1, No.26, pp. 7630-8, 2013.

[19] M. R. Hoffmann, S. T. Martin, W. Y. Choi, and D. W. Bahnemann, "Environmental applications of semiconductor photocatalysis", *Chemical Reviews*, Vol. 95, No. 1, pp. 69-96, 1995.

[20] X. Z. Li, and F. B. Li, "Study of Au/Au³⁺-TiO₂ photocatalysts toward visible photooxidation for water and wastewater treatment", *Environmental science & technology*, Vol. 35, No.11, pp. 2381-7, Jun 2001.

[21] Y. L. Pan, S. Z. Deng, L. Polavarapu, N. Y. Gao, P. Y. Yuan, and C. H. Xu, "Plasmon-enhanced photocatalytic properties of Cu₂O nanowire-Au nanoparticle assemblies", *Langmuir*, Vol. 28, No.33, pp.12304-10, Aug 2012.

[22] D. M. Schaad, B. Feng, and E. T. Yu, "Enhanced semiconductor optical absorption via surface plasmon excitation in metal nanoparticles", *Applied Physics Letters*, Vol. 86, No.6, pp. 063-106, Feb 2005.

[23] H. Phattepur, G. B. Siddaiah, and N. Ganganagappa, "Synthesis and characterisation of mesoporous TiO₂ nanoparticles by novel surfactant assisted sol-gel method for the degradation of organic compounds", *Periodica Polytechnica Chemical Engineering*, Vol. 63, No.1, pp. 85-95, 2019.

[24] S. Song, H. Yang, C. Zhou, J. Cheng, Z. Jiang, Z. Lu, and J. Miao, "Underwater superoleophobic mesh based on BiVO₄ nanoparticles with sunlight-driven self-cleaning property for oil/water separation", *Chemical Engineering Journal*, Vol. 320, pp.342-51, Jul 2017.

[25] U. M. García-Pérez, S. Sepúlveda-Guzmán, and A. Martínez-De La Cruz, "Nanostructured BiVO₄ photocatalysts synthesized via a polymer-assisted coprecipitation method and their photocatalytic properties under visible-light irradiation", *Solid State Sciences*, Vol. 14, No.3, pp. 293-8, Mar 2012.

[26] P. L. Hower, and T. K. Gupta, "A barrier model for ZnO varistors", *Journal of Applied Physics*, Vol. 50, No. 7, pp. 4847-55, Jul 1979.

[27] R. Wahab, S. G. Ansari, Y. S. Kim, H. K. Seo, G. S. Kim, G. Khang, and H. S. Shin, "Low temperature solution synthesis and characterization of ZnO nano-flowers", *Materials Research Bulletin*. Vol.42, No.9, pp.1640-8, Sep 2007.

[28] Udayabhanu, G. Nagaraju, H. Nagabhushana, R. B. Basavaraj, G. K. Raghun, D. Suresh, H. Rajanaika, and S. C. Sharma, "Green, nonchemical route for the synthesis of ZnO superstructures, evaluation of its applications toward photo-catalysis, photoluminescence, and bio-sensing", *Crystal Growth & Design*. Vol.16, No.12, pp. 6828-40, Nov 2016.

[29] D. Suresh, P. C. Nethravathi, Udayabhanu, H. Rajanaika, H. Nagabhushana, and S. C. Sharma. "Green synthesis of multifunctional zinc oxide (ZnO) nanoparticles using Cassia fistula plant extract and their photodegradative, antioxidant and antibacterial activities", *Materials Science in Semiconductor Processing*, Vol. 31, pp.446-54, Mar 2015.

[30] D. Suresh, P. C. Nethravathi, K. Lingaraju, H. Rajanaika, S. C. Sharma, and H. Nagabhushana, "EGCG assisted green synthesis of ZnO nanopowders: Photodegradative, antimicrobial and antioxidant activities", *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, Vol. 136, pp.1467-74, Feb 2015.

- [31] H. R. Madan, S. C. Sharma, D. Suresh, Y. S. Vidya, H. Nagabhushana, H. Rajanaik, K. S. Anantharaju, S. C. Prashantha, and P. S. Maiya, "Facile green fabrication of nanostructure ZnO plates, bullets, flower, prismatic tip, closed pine cone: their antibacterial, antioxidant, photoluminescent and photocatalytic properties", *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, Vol.152, pp. 404-16, Jan 2016.
- [32] A. A. Khodja, T. Sehili, J. F. Pilichowski, and P. Boule, "Photocatalytic degradation of 2-phenylphenol on TiO₂ and ZnO in aqueous suspensions", *Journal of Photochemistry and Photobiology A: Chemistry*, Vol. 141, No. 2-3, pp. 231-9, Jul 2001.
- [33] S. P. Vinay, and N. Chandrasekhar, "Facile green chemistry synthesis of ag nanoparticles using areca catechu extracts for the antimicrobial activity and photocatalytic degradation of methylene blue dye", *Materials Today: Proceedings*, Vol. 9, pp.499-505, Jan 2019.
- [34] S. P. Vinay, Udayabhanu, G. Nagarju, C. P. Chandrappa, and N. Chandrasekhar, "Enhanced photocatalysis, photoluminescence, and anti-bacterial activities of nanosize Ag: green synthesized via Rauvolfia tetraphylla (devil pepper)", *SN Applied Sciences*, Vol. 1, No. 4, pp. 477, May 2019.
- [35] J. Liqiang, S. Xiaojun, X. Baifu, W. Baiqi, C. Weimin, and F. Honggang, "The preparation and characterization of La doped TiO₂ nanoparticles and their photocatalytic activity", *Journal of Solid State Chemistry*, Vol.177, No.10, pp. 3375-82, Oct 2004.
- [36] A. Mills, R. H. Davies, and D. Worsley, "Water purification by semiconductor photocatalysis", *Chemical Society Reviews*, Vol. 22, No.6, pp. 417-25, Jan 1993.
- [37] A. Lassoued, M. S. Lassoued, B. Dkhil, S. Ammar, and A. Gadri, "Photocatalytic degradation of methyl orange dye by NiFe₂O₄ nanoparticles under visible irradiation: effect of varying the synthesis temperature", *Journal of Materials Science: Materials in Electronics*, Vol. 29, No. 9, pp. 7057-67, May 2018.
- [38] Q. Xiang, J. Yu, and P. K. Wong, "Quantitative characterization of hydroxyl radicals produced by various photocatalysts", *Journal of Colloid and Interface Science*, Vol. 357, No.1, pp. 163-7, May 2011.
- [39] G. Nagaraju, H. Nagabhushana, D. Suresh, C. Anupama, G. K. Raghunath, and S. C. Sharma, "Vitis labruska skins extract assisted green synthesis of ZnO super structures for multifunctional applications", *Ceramics International*, Vol. 43, No. 15, pp. 11656-67, Oct 2017.
- [40] G. Nagaraju, S. A. Prashanth, M. Shastri, K. V. Yathish, C. Anupama, and D. Rangappa, "Electrochemical heavy metal detection, photocatalytic, photoluminescence, biodiesel production and antibacterial activities of Ag-ZnO nanomaterial", *Materials Research Bulletin*, Vol. 94, pp. 54-63, Oct 2017.